

Ceria co-doping: synergistic or average effect?

Cite this: *Phys. Chem. Chem. Phys.*,
2014, **16**, 8320

Mario Burbano,^{*a} Sian Nadin,^a Dario Marrocchelli,^b Mathieu Salanne^c and
Graeme W. Watson^{*a}

Received 27th February 2014,
Accepted 28th February 2014

DOI: 10.1039/c4cp00856a

www.rsc.org/pccp

Ceria (CeO₂) co-doping has been suggested as a means to achieve ionic conductivities that are *significantly* higher than those in singly doped systems. Rekindled interest in this topic over the last decade has given rise to claims of much improved performance. The present study makes use of computer simulations to investigate the bulk ionic conductivity of rare earth (RE) doped ceria, where RE = Sc, Gd, Sm, Nd and La. The results from the singly doped systems are compared to those from ceria co-doped with Nd/Sm and Sc/La. The pattern that emerges from the conductivity data is consistent with the dominance of local lattice strains from individual defects, rather than the synergistic co-doping effect reported recently, and as a result, no enhancement in the conductivity of co-doped samples is observed.

1 Introduction

Distributed generation of electricity has been touted by national and international agencies, such as the Organisation for Economic Co-operation and Development (OECD),^{1–3} as a possible means to incorporate nascent technologies into the energy market. Some of these technologies rely on renewable sources, *e.g.* wind and solar, but they are still severely limited by high production costs. For this reason, more established technologies continue to attract significant attention. One such technology is called combined heat and power (CHP) where the excess heat generated in electricity production is recycled to improve the overall efficiency of the process. CHP systems have traditionally made use of steam turbines, gas turbines, reciprocating engines and, more recently, solid oxide fuel cells (SOFCs).⁴ The latter are particularly interesting given their high efficiency (up to 85%), low pollutant emissions and fuel flexibility (they can utilize hydrogen, natural gas, landfill gas, gasified coal, *etc.*⁵); thus, SOFCs have the potential to play a key role in the energy conversion landscape for the medium and long term future.^{6–9} Commercial applications of SOFCs could range from domestic units to small power stations. Nonetheless, widespread use of SOFCs has been held back by their high operating temperature, which requires the use of expensive materials and affects the long-term performance of these devices. Substantial research efforts have been devoted to lowering their operating regime to between 500 and 750 °C, known as the

intermediate temperature (IT) range.¹⁰ There are two processes which limit significantly the performance of IT-SOFCs, namely the oxygen reduction reaction (ORR) at the cathode and the ionic conductivity of the electrolyte. This article focuses on the latter effect as a means to improve the performance of SOFC electrolytes, in particular those based on doped ceria (CeO₂).

Fluorite-structured materials, such as CeO₂, ZrO₂ and δ-Bi₂O₃, are among the best oxide ion conductors, which makes them ideal candidates for use as electrolytes in IT-SOFCs. The conduction mechanism in these ceramics is known to occur by means of vacancy migration in the anion sublattice.^{11,12} Oxygen vacancies are introduced by doping these materials with lower valent cations.† For example, CeO₂ is usually doped with rare earth cations (RE = lanthanides + Sc and Y) which leads to the formation of one vacancy (V_O^{••}) for each pair of cations, as illustrated by eqn (1) in Kröger–Vink notation:¹⁴



The formation of oxygen vacancies has a beneficial effect on the conductivity, which shows, at first, a marked increase as more vacancies are added. This increase, however, does not display a monotonic behaviour, but rather, a sharp drop in conductivity is observed beyond a critical concentration. In the case of ceria, this value varies between 2.5 and 5% vacancy concentration, depending on the dopant cation species, the temperature and other factors. There is a general consensus that this drop in conductivity with increased number of vacancies is caused by defect–defect interactions.^{15–24} The interactions between these defects can be broadly classified into cation–vacancy, vacancy–vacancy and

^a School of Chemistry and CRANN, Trinity College Dublin, Dublin 2, Ireland.

E-mail: burbanom@tcd.ie, watson@tcd.ie; Tel: +353-18961357

^b Department of Nuclear Science and Engineering,

Massachusetts Institute of Technology, Cambridge, MA, USA

^c Sorbonne Universités, UPMC Univ Paris 06, CNRS, UMR 8234, PHENIX,
F-75005 Paris, France

† δ-Bi₂O₃ actually behaves differently, since this material already has 25% intrinsic vacancies. In this case doping with iso-valent cations is used to stabilise the fluorite structure at low temperatures.¹³

cation–cation.^{15–22} In practice, these interactions can prove deleterious to the ionic conductivity because defect association leads to fewer mobile vacancies being available,²³ thus the need for high operating temperatures. This process is generally summarised by the following formula for the conductivity, σ :

$$\sigma T = \sigma_0 \exp\left(-\frac{E_a}{k_B T}\right), \quad (2)$$

where T is the temperature, σ_0 the composition-dependent pre-exponential factor, E_a the activation energy and k_B the Boltzmann constant. The activation energy is given by the sum of the migration enthalpy, ΔH_m , and the defect association enthalpy, ΔH_{ass} . The higher the association enthalpy, the lower the conductivity.

Traditionally, ionic conductivity optimization has been approached from a compositional perspective. This has meant that, in order to improve the conductivity of ceria-based electrolytes, researchers have mostly focused on parameters such as the ionic radius of the dopant cation and its concentration, x in $\text{Ce}_{1-x}\text{RE}_x\text{O}_{2-x/2}$. The chief aim has been to minimize defect interactions, especially those between dopants and vacancies.^{16,25–29} These studies have variously identified a number of RE elements, such as Gd^{3+} , Y^{3+} , Sm^{3+} and Pm^{3+} , as the best candidate dopants, given that their radius mismatch with the host cation (Ce^{4+}) balances the competing electrostatic and elastic components of the defect interactions which control their association.³⁰ Nevertheless, recent studies have shown that in the limit where cation–vacancy interactions are reduced to a minimum, it is vacancy–vacancy association which ultimately determines the ionic conductivity drop as a function of dopant concentration in fluorite-structured materials, such as yttria doped ceria (YDC),²² yttria stabilized zirconia (YSZ) and scandia stabilized zirconia (ScSZ).²¹ This means that different optimization strategies must be sought if IT-SOFCs are to realize their potential in commercial applications.^{6,7,31,32}

An interesting route for improving the ionic conductivity of fluorite-structured electrolytes is co-doping, *i.e.* doping these materials with more than one cation species. This approach was employed on ZrO_2 by Politova and Irvine³³ with two different cation species, each playing a different role. In this case, the material was doped with two different cation species, where each of which played a *different* role. Sc was added to improve the ionic conductivity, since its radius is very close to that of Zr, thus minimizing cation–vacancy interactions, while Y, on the other hand, was introduced because its larger ionic radius fully stabilizes the fluorite structure and removes phase transition to a lower-symmetry phase observed in pure Sc-doped ZrO_2 . It is important to note that Y addition to Sc-doped ZrO_2 *lowers* the conductivity of this material. Therefore, a *compromise* exists between stability and ionic conductivity in this co-doped zirconia system. In the case of Politova and Irvine, the authors found that very *small* concentrations of Y are necessary to stabilize the cubic fluorite structure and that this has a small effect on the conductivity.

It has been suggested that co-doping can also be used to improve the ionic conductivity of ceria based electrolytes.^{34–46} However, contrary to the stabilizing role it plays in zirconia,

co-doping in ceria has been used in order to reproduce either the ionic radius of an ideal dopant or the lattice constant of ceria doped with said dopant. Co-doping with two or more different cations aims to obtain an *average* or “effective” cation radius that is very close to that of Ce^{4+} ; hence the average strain introduced by the dopant cations is minimized. This is substantiated by different interpretations of how a dopant with a critical radius (r_c) is likely to affect defect–defect interactions. For example, in 1989 Kim suggested that the ideal dopant would not change the volume of the host lattice upon its introduction, thus minimizing the elastic strain, and identified $r_c = 1.038 \text{ \AA}$.⁴⁷ More recently, researchers have had access to a more detailed view of the interplay between strain and electrostatics with the use of *ab initio* methods, which in 2006 led Andersson *et al.*²⁹ to ascertain that r_c should be that which maximizes oxygen vacancy disorder. Their simulations showed that when ceria is doped with relatively small cations, vacancies prefer to sit in a nearest neighbour (NN) position with respect to the dopant cation, whereas, for larger cations, vacancies prefer to sit in a next nearest neighbour (NNN) position. The crossover between these two tendencies was observed at Pm^{3+} , for which the NN and NNN positions have the same energy, which was rationalized in terms of a perfect balance between the elastic (related to the dopant’s radius) and Coulombic interactions between Pm^{3+} and a vacancy. This finding implies that Pm^{3+} is the ideal dopant for ceria because it increases the configurational entropy and should display the highest ionic conductivity. Unfortunately, Pm^{3+} is radioactive, so the authors suggested, instead, to try a mixture of Sm/Nd which have slightly smaller/larger ionic radii than Pm^{3+} .[‡] Based on these ideas, multiple research groups have carried out experiments in order to test several co-doping schemes for ceria, *e.g.* Y/Sm co-doping,³⁹ La/Y co-doping,⁴⁰ Lu/Nd co-doping⁴⁹ and Sm/Nd co-doping,³⁸ of which the latter two were specifically aimed at reproducing the r_c values predicted by Kim and by Andersson, respectively. In general, co-doping studies have pointed to increases in the ionic conductivity with respect to singly doped systems, which has led to the conclusion that there exists a “co-doping” effect in ceria.

Modern simulation techniques have become a mainstay within the materials science community, not only because they afford researchers information which is complementary to their experiments, but also because they can serve as predictive tools.⁵⁰ Hence, the implementation of reliable computer simulations can be used to clarify the role of particular effects present in physical experiments in a targeted and controlled manner. To this end, the interaction potentials reported here are shown to perform with the accuracy of state-of-the-art *first-principles* calculations, *i.e.* hybrid density functional theory (DFT), but at the computational cost of classical (polarizable) molecular dynamics. This approach allows us to study systems with realistic doped/co-doped defect concentrations within the temperatures of interest

‡ We note here that the radii of these three elements (1.079, 1.093, and 1.109 Å for Sm, Pm and Nd, respectively⁴⁸) are all very similar and almost within the associated experimental error.

for SOFC applications (600–1000 °C), and to accumulate sufficiently long trajectories to calculate the conductivity. This is in contrast to most of the previous computational work on doped ceria which has typically used static DFT calculations or empirical potentials fitted to equilibrium properties.^{25,51} The use of computer simulations allows us to focus on the *bulk* behaviour of this material, excluding factors like grain size and boundaries, sintering conditions, impurity levels, *etc.*, which are also known to (negatively) affect the conductivity of these materials.^{52,53} We show that co-doping does not significantly improve the conductivity of these materials, but rather, we find that the conductivity of the co-doped systems lies within the range spanned by the singly doped systems, *i.e.* it is an average of the two. The reason for this is that introducing two cation species with radii which are bigger or smaller than that of a given r_C affects the local structure of ceria and results in deep traps for the vacancies.

2 Methods

2.1 Interionic potential

The highly correlated nature of the f-electrons found in lanthanide elements makes necessary the use of high levels of theory in order to correctly describe their electronic structure. Such demands have been found to be satisfied by the inclusion of a fraction of non-local Hartree–Fock exchange within the framework of density functional theory (DFT), which gives rise to hybrid functionals (h-DFT).^{54–56} Alternative DFT functionals are also available, namely, those which include a Hubbard parameter U (DFT + U). They represent a viable alternative to h-DFT and their ability to describe the properties of ceria has been widely documented.^{57–61} Nonetheless, h-DFT provides a better agreement with experimental lattice constants and does not require fitting a + U value for the f-electron systems. In either case, however, DFT calculations are prohibitively expensive from a computational point of view for this type of study regardless of the functional; this is because of the long molecular dynamics (MD) simulation times and large systems required to study the ionic conductivity of doped ceria. For this reason interionic potentials (IP) implemented in an in-house MD code (PIMAIM)⁶² and derived from static h-DFT calculations were used in this work, as they accurately reproduce the structural *ab initio* data at a fraction of the computational cost. This approach has been successfully used for a series of related oxides,^{20,21,63–67} including Y-doped ceria,^{22,68} as well as a variety of ionic systems.^{69–71} The RE dopant cations studied in this article included La, Nd, Sm and Gd, as well as Sc. A crucial feature of this potential set is that they were fitted with a *common* O–O term, which made it possible to perform simulations with several dopant cations within the same cell, *i.e.* to co-dope ceria. Details on the interionic potential used (DIPPIM – dipole polarizable ionic model), and its parameterization and the parameters used are found in Appendix A and Appendix B, respectively.

2.2 Simulation details

All MD simulations on the singly doped $Ce_{1-x}RE_xO_{2-x/2}$ and co-doped systems were performed using $6 \times 6 \times 6$ supercells (~ 2592 atoms, depending on the dopant concentration).

Two different co-doped systems formed part of this study. Firstly, $Ce_{1-x}Nd_{0.5x}Sm_{0.5x}O_{2-x/2}$, which has been previously studied experimentally,³⁸ was included because the average radius of both dopants matches that of Pm. Similarly, $Ce_{1-x}Sc_{0.22x}La_{0.78x}O_{2-x/2}$ was included given that this ratio of La and Sc also reproduces the ionic radius of Pm. Three different supercells were set up for each dopant concentration, $x = 0.05, 0.10, 0.15, 0.20,$ and 0.25 , and the values reported here, such as ionic conductivities, lattice constants and activation energies, were obtained from the averages of these three configurations. Each calculation was set up by randomly distributing the dopants over the cation sublattice and the oxygen vacancies over the anion sublattice. The supercells were initially equilibrated at a temperature of 1673 K for 40 ps; the temperature was then scaled down to room temperature at a rate of 2 K ps^{-1} . The diffusion coefficients were calculated for temperatures between 873 K and 1473 K from simulations that were up to 3 ns long in the case of the lowest temperature. The 300 K lattice constants were obtained from 10 ps long runs. All simulations were performed at constant temperature and pressure (NPT ensemble), as described by Martyna *et al.*,⁷² using a time step of 1 fs. The Coulombic and dispersion interactions were summed using Ewald summations,⁷³ while the short-range part of the potential was truncated at 12.96 Å.

3 Results and discussion

The reliability of the models used in the computer simulations presented throughout this work is assessed in Section 3.1 by means of comparison against experimental and computational results for singly doped ceria. We also note that this approach has already been successfully used to model yttria-doped ceria, as reported in ref. 68. Section 3.2 builds upon these results to determine whether co-doping is likely to improve the ionic conductivity in these solid electrolytes. The remainder of this article abbreviates the various RE-doped ceria systems ($Ce_{1-x}RE_xO_{2-x/2}$) under study as ScDC, GdDC, SmDC, NdDC and LaDC. In a similar fashion, the co-doped systems are referred to as Sc:LaDC and Nd:SmDC.

3.1 Potential assessment

3.1.1 Lattice constants of singly doped ceria. The DIPPIM simulated lattice constants for $Ce_{0.90}RE_{0.10}O_{1.95}$ at 300 K are shown in Fig. 1 as a solid black line. Their associated errors are represented by the standard deviation of the values from the three simulations carried out for each system. The dashed red line in Fig. 1 corresponds to the values for the same systems predicted by Hong and Virkar,⁷⁴ who derived an empirical expression for the relationship between the ionic radius of the dopant and the lattice constant of RE-doped ceria. Fig. 1 also presents experimental (open symbols) and computational (closed symbols) lattice constant values for the same compositions (10% cation doped) of ScDC, GdDC, SmDC, NdDC and LaDC.

As shown in a previous study by the authors,²² DIPPIM simulations are expected to perform as well as the DFT functional from which they were parameterized. In this case, the use of

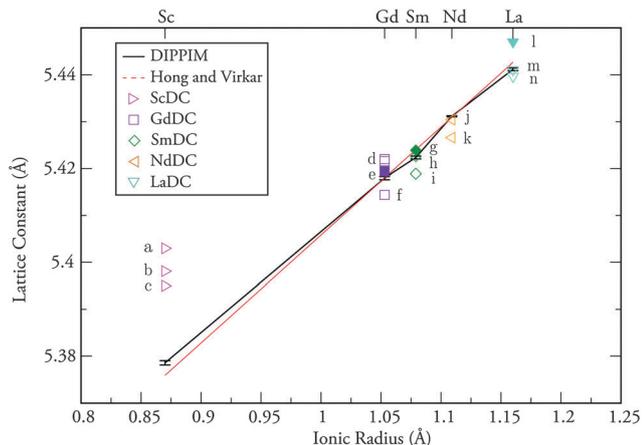


Fig. 1 Lattice constants for $\text{Ce}_{0.90}\text{RE}_{0.10}\text{O}_{1.95}$. DIPPIM values at 300 K (this work) are shown as a solid black line. The errors correspond to the standard deviation obtained from three simulations. Hong and Virkar⁷⁴ values are represented by a dashed red line. Literature data from (a) Grover *et al.*,⁷⁵ (b) Lee *et al.*,⁷⁶ (c) Gerhardt-Anderson and Nowick,⁷⁷ (d) Huang *et al.*,⁷⁸ and Zhang *et al.*,⁷⁹ (e) Huang *et al.*,⁸⁰ (f) Omar *et al.*,³⁷ (g) Huang *et al.*,⁸⁰ (h) Buyukkilic *et al.*,⁸¹ (i) Omar *et al.*,³⁷ (j) Buyukkilic *et al.*,⁸¹ (k) Omar *et al.*,³⁷ (l) Huang *et al.*,⁸⁰ (m) Hisashige *et al.*⁸² and (n) Dikmen *et al.*⁸³

hybrid DFT functionals means that errors in the calculated value of lattice constants with respect to experiment for doped ceria should be in the order of 0.20%.⁵⁴ This is borne out by the results presented in Fig. 1, which show an excellent agreement with the range of experimental data available in the literature and also with the values calculated using Hong and Virkar's equation. In the case of ScDC, the simulations provide a better estimation of the lattice constant than that obtained from Hong and Virkar with respect to experiment; however both models underestimate the value of a_0 . For DIPPIM simulations of ScDC, the largest error is 0.45% compared to the value from Grover *et al.*⁷⁵ Despite this being a relatively small error, it is likely that this discrepancy arises from sources other than the DFT functional employed in this work. In fact, of the three experimental sources cited, Grover *et al.* (highest value for a_0), as well as Gerhardt-Anderson and Nowick⁷⁷ (lowest value for a_0), predict low solubilities for scandia (Sc_2O_3) and, thus, formation of C-type phases in $\text{Ce}_{0.90}\text{Sc}_{0.10}\text{O}_{1.95}$ which are characteristic of sesquioxides that crystallize in the cubic bixbyite structure, such as scandia. This phase separation in $\text{Ce}_{0.90}\text{Sc}_{0.10}\text{O}_{1.95}$ was recently demonstrated by a series of elegant simulations that coupled DFT + U and Monte Carlo simulations.⁸⁴

3.1.2 Ionic conductivity of singly doped ceria. The ionic conductivities calculated for all the singly doped ceria systems under study are presented in Fig. 2. The conductivities from simulations at 1273 K are indicated by the dashed lines, those at 1073 K by dotted lines and those at 873 K by solid lines. These lines are to be interpreted only as a guide to the eye, as they connect the individual values from the calculations, each of which has an associated error indicated by the standard deviation from three measurements. The colours differentiate the concentration of the dopant cations as a percentage; thus 5% is shown in black, 10% in blue, 15% in orange, 20% in green and

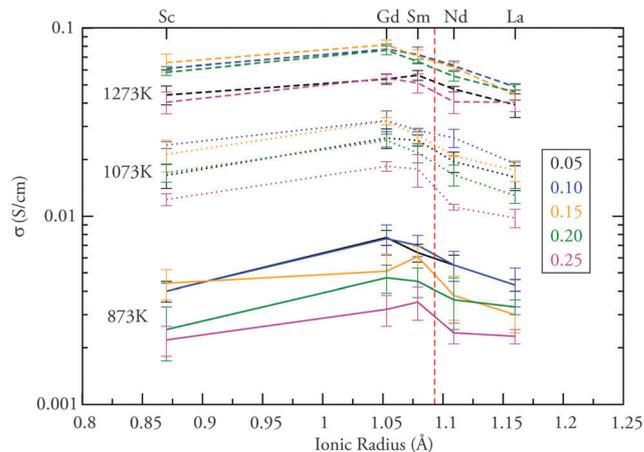


Fig. 2 Ionic conductivities for singly doped ceria ($\text{Ce}_{1-x}\text{RE}_x\text{O}_{2-x/2}$) at 1273 K (blue diamonds), 1073 K (black dots) and 873 K (red triangles). The vertical dashed red line represents the critical ionic radius (r_c) introduced by Andersson *et al.*²⁹

25% in magenta. In agreement with the literature for singly doped ceria, the best dopants were found to be Gd and Sm.^{25,81,85} In particular, GdDC was found to have the highest conductivity at all temperatures. The results also show that the concentration which gives the highest conductivity varies from one doped system to another for a particular temperature. However 10% GdDC is consistently among the systems that display the highest conductivity. In addition, the errors associated with each measurement become larger at lower temperatures because of the slower diffusion. As mentioned above, Sc is soluble in ceria only in small amounts; hence the results presented here for a fluorite structure with randomly distributed cations correspond to an idealized description of ScDC. The dashed red line (vertical) shown in Fig. 2 represents Andersson's critical ionic radius²⁹ (r_c) for the ideal dopant cation.

Fig. 3 focuses on the DIPPIM simulated ionic conductivities at 873 K for the systems already presented and puts them in the context of a range of conductivity values from other studies for the same singly doped ceria ($\text{Ce}_{0.90}\text{RE}_{0.10}\text{O}_{1.95}$) systems at the same temperature. The value for Sc is not included in this plot as there are no data available in the literature for the selected concentration and temperature. Individual literature values are labelled (a) to (m), with open symbols indicating experimental values and filled symbols those from other computational studies. This figure shows that there is a significant spread in the experimental data set, as exemplified by GdDC, whose conductivities vary by a factor of 2.5 (from 0.01 S cm^{-186} to $0.025 \text{ S cm}^{-185}$). Such fluctuations are typically ascribed to different fabrication methods, sintering times and temperatures, grain sizes and impurities,^{85,86} all of which are excluded from our computational bulk models. Nonetheless, what is clear from Fig. 3 is that the DIPPIM potentials used in this work deliver conductivity values which lie in the lower end of the range of the experimental ones, but constitute a good predictor of the overall tendencies in doped ceria.

The calculated E_a values for these systems are shown in Fig. 4 (filled black circles) as a function of dopant ionic radius

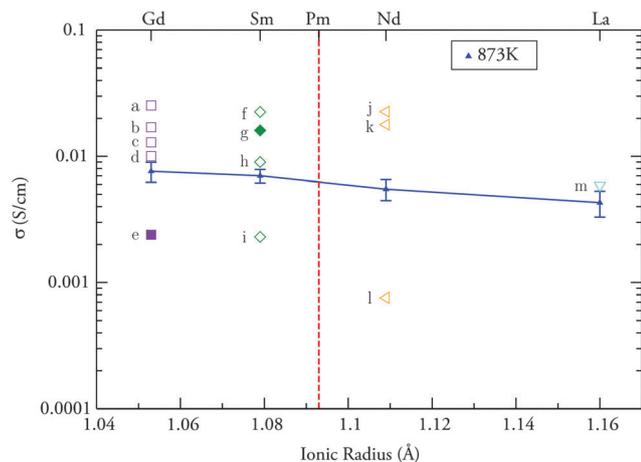


Fig. 3 Ionic conductivities for $\text{Ce}_{0.90}\text{RE}_{0.10}\text{O}_{1.95}$ at 873 K (blue triangles). Open symbols correspond to experimental values, while filled symbols were obtained from computational data in the literature: (a) Steele,⁸⁵ (b) Huang *et al.*⁷⁸ and Omar *et al.*,³⁸ (c) Xia and Liu,⁸⁷ (d) Zhou *et al.*,⁸⁶ (e) Dholabhai *et al.*,⁸⁸ (f) Kasse and Nino,⁴⁶ (g) Grope *et al.* (at 893 K)⁸⁹ and Omar *et al.*,³⁷ (h) Shemilt and Williams,⁹⁰ (i) Jung *et al.*,⁹¹ (j) Kasse and Nino,⁴⁶ (k) Omar *et al.*,³⁷ (l) Aneflou *et al.*⁹² and (m) Dikmen *et al.*⁸³ The vertical dashed red line represents the critical ionic radius (r_c) introduced by Andersson *et al.*²⁹

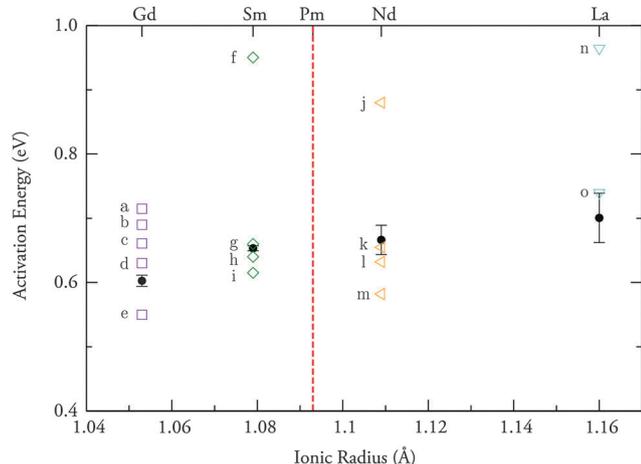


Fig. 4 Activation energies from this work (filled black circles) between 1473 K and 873 K for $\text{Ce}_{0.90}\text{RE}_{0.10}\text{O}_{1.95}$. Open symbols correspond to experimental values: (a) Zhang *et al.*,⁹³ (b) Omar *et al.*,³⁸ (c) Omar *et al.*,³⁷ (d) Huang *et al.*,⁷⁸ (e) Xia and Liu,⁸⁷ (f) Jung *et al.*,⁹¹ (g) Shemilt and Williams,⁹⁰ (h) Omar *et al.*,³⁷ (i) Kasse and Nino,⁴⁶ (j) Aneflou *et al.*,⁹² (k) Omar *et al.*,³⁷ (l) Kasse and Nino,⁴⁶ (m) Stephens and Kilner,⁹⁴ (n) Lang *et al.*⁹⁵ and (o) Dikmen *et al.*⁸³ The dashed red line represents the critical ionic radius (r_c) introduced by Andersson *et al.*²⁹

and were obtained from simulations between 1473 K and 873 K. The plots of $\ln(\sigma T)$ vs. $1/T$ within this range of temperatures were found to be linear for all dopants. This is important as it indicates that there is no extensive clustering of dopants and vacancies, which would occur if the simulations spanned both sides of the critical temperature (T^*) below which nucleation centres form around the dopants leading to progressive trapping of the vacancies into such clusters as the temperature decreases.^{52,78}

If the calculations had been carried out at sufficiently low temperatures ($T^* \approx 856$ K for GdDC⁷⁸), then two different E_a values would have been obtained for the $T > T^*$ and $T < T^*$ temperature regimes. For this reason, the literature data presented in Fig. 4 correspond to the $T > T^*$ region only. Experimental values are distinguished with the same open symbols from Fig. 3 and labelled (a) to (o). Just as was found to be the case with ionic conductivities, Fig. 4 illustrates that the self-consistent DIPPIM potentials used in this work are able to predict the activation energies for the various RE dopants used in this study. This is particularly impressive since no experimental data were used at any stage of the potential parameterization. We can therefore proceed to study co-doping in this material, with the confidence that the employed simulation technique can reliably predict the properties of these materials. The predicted E_a for $\text{Ce}_{0.90}\text{Sc}_{0.10}\text{O}_{1.95}$ is 0.675 eV.

3.2 Co-doped ceria

3.2.1 Lattice constants of co-doped ceria. Fig. 5 presents the DIPPIM calculated (filled symbols) and experimental lattice constants (open symbols) from Buyukkilic *et al.*⁸¹ at 300 K for $\text{Ce}_{1-x}\text{RE}_x\text{O}_{2-x/2}$, where $x = 0.05, 0.10, 0.15, 0.20,$ and 0.25 and RE = Sm, Nd, Nd:SmDC and Sc:LaDC. The co-doped systems shown correspond to an effective dopant cation radius of 1.093 Å for the stoichiometries specified in Section 2.2. It is evident from the figure that the calculations predict the correct lattice constant for the singly doped systems over the entire composition range, and that this carries over to the co-doped cerias under study. The agreement is particularly good for the systems that are the focus of this study, namely $\text{Ce}_{0.90}\text{RE}_{0.10}\text{O}_{1.95}$. The results show that co-doping can be successfully used to reproduce the lattice constant of a cation with a critical dopant radius, r_c .

3.2.2 Ionic conductivity of co-doped ceria. Thus far the results presented for the ionic conductivity of singly doped

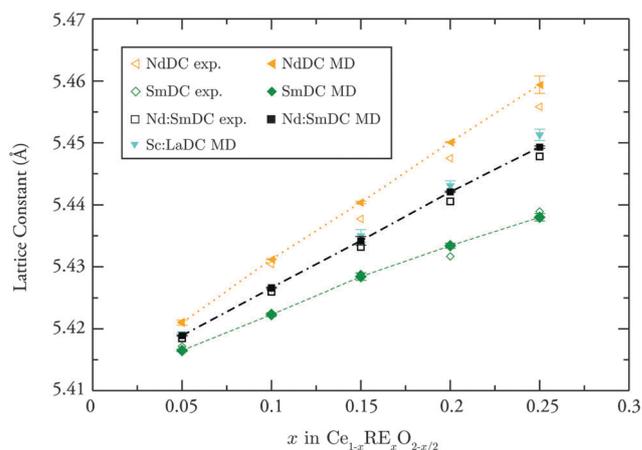


Fig. 5 DIPPIM calculated (filled symbols) and experimental (open symbols) lattice constants from Buyukkilic *et al.*⁸¹ at 300 K for $\text{Ce}_{1-x}\text{RE}_x\text{O}_{2-x/2}$, where $x = 0.05, 0.10, 0.15, 0.20,$ and 0.25 and RE = Sm (diamonds), Nd (triangles pointing left), Nd:SmDC (squares) and Sc:LaDC (triangles pointing down). The lines shown are intended as a guide to the eye only.

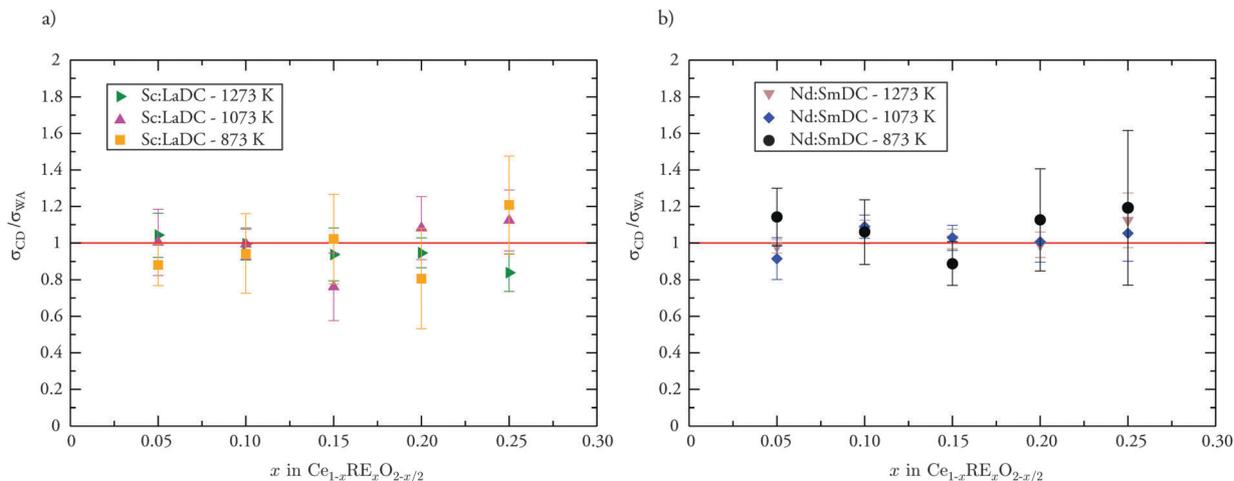


Fig. 6 DIPPIM ionic conductivities shown as a ratio of the values for co-doped (CD) ceria and the weighted average (WA) of their singly doped parent oxides. Panel (a) corresponds to the Sc:LaDC system and panel (b) corresponds to Nd:SmDC.

ceria have shown only progressive changes in both the bulk ionic conductivities and activation energies as a function of dopant ionic radius. Hence, the question of whether co-doping is a viable alternative for substantially improving these properties becomes: *Do co-doped systems show a marked increase (decrease) in ionic conductivity (activation energy) or is this property simply the average of the values obtained for singly doped systems?*

To answer this question it is necessary to compare directly the ionic conductivity of the co-doped systems with that of their “parent” singly doped ceria compounds. Hence if there exists a co-doping effect it would be expected that such systems display ionic conductivities that are higher than the average of the values obtained for singly doped ceria. These data are shown in Fig. 6(a) for the Sc:LaDC system and Fig. 6(b) for Nd:SmDC. The data in these plots are presented as a ratio of the calculated conductivities for the co-doped systems (σ_{CD}) and the weighted average for the singly doped parent compounds with the same total number of dopant cations (σ_{WA}). The weighting factors are given by the ratio of each co-dopant as specified in Section 2.2, namely 0.50 for both Nd and Sm in Nd:SmDC, as well as 0.22 and 0.78 for Sc and La, respectively, in Sc:LaDC. The solid red line indicates a linear correspondence between both data sets (co-doped vs. weighted average of singly doped), *i.e.* no co-doping effect. It is clear from these plots that any deviations in σ_{CD} away from the σ_{WA} values are within the margin of error of these measurements (standard deviation). This indicates that the conductivities of co-doped ceria can be predicted by simply calculating the average of the conductivities of two parent singly doped cerias for all temperatures and dopant concentrations.

Accordingly, it is expected that the corresponding activation energies for the ionic conductivity of co-doped ceria display the same averaging effect. This is confirmed in Fig. 7, which depicts the DIPPIM E_a (eV) for $Ce_{0.90}RE_{0.10}O_{1.95}$ from Fig. 4 (filled black circles), along with those for the co-doped systems Nd:SmDC (filled blue triangle) and Sc:LaDC (filled black triangle). Experimental values are from (a) Omar *et al.*³⁷ (open squares) and (b) Kasse and Nino⁴⁶ (open circles), with green for SmDC, maroon for Nd:SmDC and orange for NdDC.

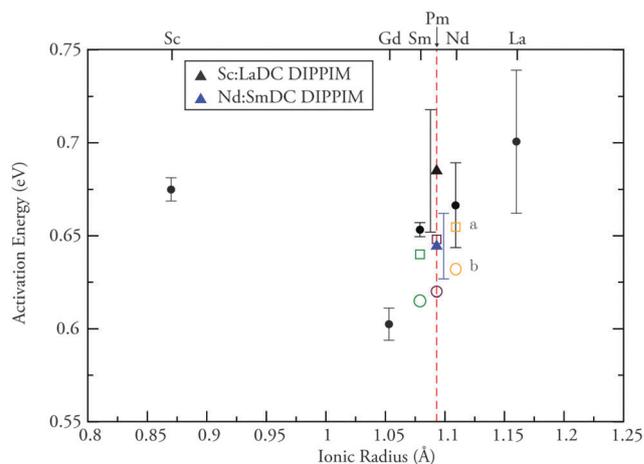


Fig. 7 DIPPIM activation energies (eV) for $Ce_{0.90}RE_{0.10}O_{1.95}$ from Fig. 4 along with those for the co-doped systems Nd:SmDC (filled blue triangle) and Sc:LaDC (filled black triangle). Experimental values from (a) Omar *et al.*³⁷ (open squares) and (b) Kasse and Nino⁴⁶ (open circles) with green for SmDC, maroon for Nd:SmDC and orange for NdDC.

for Nd:SmDC and orange for NdDC. Both data sets show that despite having the same effective r_C value of 1.093 Å and taking into account the errors intrinsic to these calculations, the co-doped Sc:LaDC system has a higher activation energy than Nd:SmDC; that is, the DIPPIM simulations as well as the experimental data for these co-doped systems show changes in bulk ionic conductivities and activation energies that are in line with an averaging effect with respect to the singly doped “parent” oxides, with small deviations from this behaviour likely due to sampling error. A simple, yet often overlooked, explanation for these patterns is found by analyzing the local structure around the dopants in these systems as shown in the next section.

3.2.3 Local structure of co-doped systems. A configurational analysis of the MD simulations for 10% cation doped LaDC, ScDC and Sc:LaDC is illustrated in Fig. 8 in the form of the

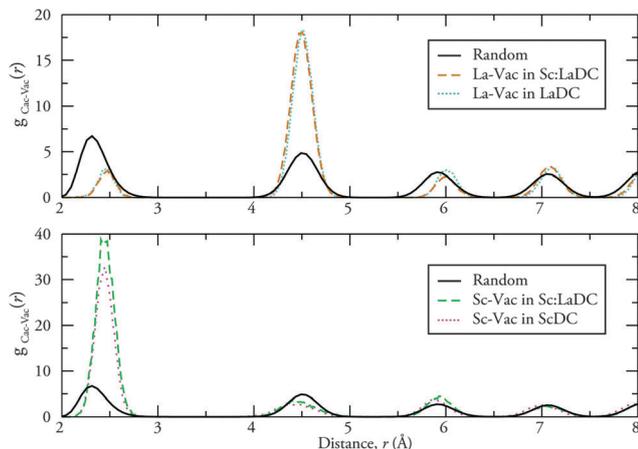


Fig. 8 Cation–vacancy partial radial distribution functions ($g_{\text{Cat-Vac}}(r)$) at 873 K. Top panel: random (solid black line), La^{3+} -vacancy in Sc:LaDC (dashed orange line) and La^{3+} -Vac in LaDC (dotted turquoise line). Bottom panel: random (solid black line), Sc^{3+} -vacancy in Sc:LaDC (dashed green line) and Sc^{3+} -vacancy in ScDC (dotted magenta line).

cation–vacancy partial radial distribution functions ($g_{\text{Cat-Vac}}(r)$) obtained from the average of the three configurations used for each system. Appendix C details the process of oxygen vacancy identification and subsequent calculation of $g(r)$. The average values are presented in order to eliminate any possible configuration-dependent ordering of the cations. The La/Sc doubly and singly doped systems are illustrated given that the large radius mismatch between the dopant cations with the host facilitates visualization of the small changes undergone; however the conclusions were confirmed for the other co-doped systems. The top panel shows the $g(r)$ s for La-Vac in Sc:LaDC (dashed orange line) vs. La-Vac in LaDC (dotted turquoise line); the bottom panel contains the $g(r)$ s for Sc-Vac in Sc:LaDC (dashed green line) vs. Sc-Vac in ScDC (dotted magenta line). The solid black lines in both panels correspond to the Ce–O $g(r)$ in bulk ceria at the same temperature, which exemplifies a random vacancy distribution, but with a slightly different lattice constant due to the absence of dopants. The number of vacancies coordinated to the cations in these systems were obtained by integrating the peaks in Fig. 8 and are reported in Table 1, with the addition of the values for GdDC of the same concentration which are included for comparison as it is the best single dopant system. These results show that Sc acts as a vacancy scavenger in ScDC, with the vacancies ordering in the first coordination shell of this cation. This is a well known effect which has been documented by experiments^{77,96} and simulations.^{25,97} In fact, dopant cations that are smaller in radius than Ce^{4+} are generally expected to have vacancies in nearest neighbour (NN) positions, while those that are larger are expected to have vacancies in the next nearest neighbour (NNN) position. The latter effect is observed in the case of the larger La and Gd (Table 1) cations as indicated by the pronounced second peak. The results in Fig. 8 and Table 1 clearly show that the local environment, and thus the local strain, of the dopant cations undergoes few changes in going from singly doped systems to those with more than one dopant species.

Table 1 Number of vacancies in the nearest neighbour (NN) and next nearest neighbour (NNN) positions with respect to the cations in a random distribution, GdDC, Sc:LaDC, LaDC and ScDC. These values were obtained from the integration of the peaks in Fig. 8

Peak	Random Ce–O	GdDC Gd–Vac	LaDC La–Vac	Sc:LaDC La–Vac	ScDC Sc–Vac	Sc:LaDC Sc–Vac
1st (NN)	0.200	0.168	0.062	0.059	0.734	0.878
2nd (NNN)	0.600	1.356	1.502	1.578	0.412	0.467

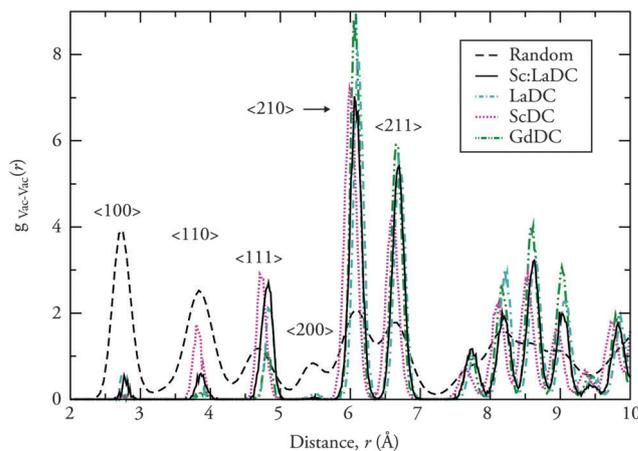


Fig. 9 Vacancy–vacancy partial radial distribution functions at 873 K for Sc:LaDC (solid black line), LaDC (dot–dashed turquoise line), ScDC (dotted magenta line), GdDC (dot–dot–dashed green line) and a random vacancy distribution (O–O $g(r)$). The $\langle 100 \rangle$, $\langle 110 \rangle$ and $\langle 111 \rangle$ labels indicate different directions along the simple cubic anion sublattice.

Previous studies have shown that concomitant with cation–vacancy ordering, there also exist inherent vacancy–vacancy ordering interactions in fluorite-structured materials.^{21,22,98,99}

Fig. 9 presents the three configuration average vacancy–vacancy partial radial distribution functions ($g_{\text{Vac-Vac}}(r)$) at 873 K for Sc:LaDC (solid black line), LaDC (dot–dashed turquoise line), ScDC (dotted magenta line), GdDC (dot–dot–dashed green line) as well as a random vacancy distribution, which is simply the O–O $g(r)$ from CeO_2 at the same temperature. The $\langle 100 \rangle$, $\langle 110 \rangle$ and $\langle 111 \rangle$, $\langle 210 \rangle$, etc. labels indicate different directions along the simple cubic anion sublattice. The values obtained upon integration of these peaks are reported in Table 2. The results show that for this dopant concentration vacancies display some degree of long range ordering as evidenced by the sharp peaks

Table 2 Number of vacancies surrounding another vacancy along the $\langle 100 \rangle$, $\langle 110 \rangle$ and $\langle 111 \rangle$ directions of the simple cubic anion sublattice of 10% cation doped GdDC, LaDC, ScDC and Sc:LaDC, as well as a random distribution of the same number of vacancies. These values were obtained from the integration of the peaks in Fig. 9

System	$\langle 100 \rangle$	$\langle 110 \rangle$	$\langle 111 \rangle$
Random	0.150	0.300	0.200
GdDC	0.001	0.010	0.056
LaDC	0.06	0.007	0.107
ScDC	0.001	0.062	0.170
Sc:LaDC	0.006	0.023	0.213

in the $\langle 210 \rangle$ and $\langle 211 \rangle$ positions, while the positions that are at shorter distance in the simple cubic lattice are underpopulated with respect to a random vacancy distribution. This effect arises from the Coulomb repulsions between the vacancies. Common to all the doped ceria systems is also a deleterious redistribution of the vacancies which favours short range occupancy along the $\langle 111 \rangle$ direction with respect to an idealized random system. This effect is larger in inferior conductors, like LaDC and ScDC, than in the better ones like GdDC, for example; in the case of Sc:LaDC, co-doping is shown to enhance this ordering, because the small Sc^{3+} cations trap the vacancies in the NN positions, while the large La^{3+} cations repel them towards NNN but also increase their migration barrier,⁹⁷ which leads to an overall increase in the vacancy ordering of co-doped systems. This indicates that the “synergistic” effect on bulk ionic conductivity from co-doping is not realized.

4 Ceria co-doping in perspective

Despite the significant improvements in the ionic conductivity of co-doped ceria reported by several previous studies^{38–42,44,49,100,101} this work found that this property is simply an average of the conductivities of singly doped materials. This is in accordance with an early experimental/computational study by Yoshida *et al.*,^{102,103} as well as recent experimental data reported in Fig. 7 for Nd:SmDC.^{37,46} Similar results were reported by Ralph *et al.* for Yb:LaDC and Sm:YDC, and by Li *et al.*⁹⁶ for Sc:GdDC, who observed a worsening in these properties for co-doped cerias with substantially mismatched dopant cations. The interpretation provided in both cases was that the localized nature of the strains caused by each dopant species does not change substantially in the co-doped systems compared to singly doped materials.

We point out that our investigation has left out a series of factors, such as long-range cation ordering, grain boundaries, impurities, *etc.*, that might also affect the total conductivity of these materials. This was done on purpose, because the focus of this investigation was on bulk properties of perfect fluorite-structured materials. We note here that these factors have usually a detrimental effect on the conductivity of these materials, so that our conclusions are not invalidated by leaving them out. For instance, cation ordering might be expected in Sc:LaDC,⁸⁴ because the cations have significantly different ionic radii. This was not taken into account in these calculations, because the cations were randomly distributed and the simulation timescale does not allow them to diffuse. Cation ordering is known to lead to a decrease of the ionic conductivity, as observed in several oxides,^{66,104} so that the effects of co-doping might be even more detrimental to the material's conductivity than what we predict in this investigation.

Finally, we wonder why many studies have found an enhancement of the ionic conductivity in some co-doped materials, while others have not. We note that, as discussed above, there are many factors (grain boundaries, cation ordering, phase separation and nano-domain formation, impurity levels, *etc.*) that affect

the ionic conductivity of these materials and it is very hard to separate their effects. As an example, the conductivity of 10% GdDC, as shown in Fig. 3, varies by as much as a factor of 2.5 in different experiments. Such a huge variation is probably caused by a combination of these factors and shows that it is not trivial to compare the conductivity of these materials.

5 Conclusions

This work was motivated by the conflicting evidence that surrounds the merits of ceria co-doping as a means to improve this electrolyte's ionic conductivity. Here we used molecular dynamics simulations that employ accurate interionic potentials, parameterized with respect to *first-principles* calculations. No experimental data were used to parameterise these potentials. This methodology allowed the study of large systems at realistic operating temperatures (~ 873 – 1273 K) and defect concentrations. The conclusions pertain only to *bulk* properties, because the models that were simulated do not include grain boundaries, impurity segregation, dislocations, *etc.*

The results show that co-doping can be successfully used to reproduce the lattice constant of ceria doped with a single cation which has an ionic radius equal to the effective radius from two co-dopants. However, close examination of the *bulk* ionic conductivity of co-doped ceria revealed that this property is not enhanced by co-doping and can be described as an average of the conductivities of the “parent” singly doped compounds. This result was explained by the fact that the vacancy ordering tendencies of individual dopant cations remain largely unchanged in co-doped systems. For this reason, co-doping with cations that are bigger/smaller than a given ideal dopant radius (r_c) leads to the combination of unwanted defect trapping tendencies, as exemplified by the case of the significantly mismatched Sc:LaDC system, where Sc^{3+} is an oxygen vacancy scavenger while La^{3+} repels vacancies. In conclusion it is the *local* structure of these materials, rather than their average structure, that dictates their conducting properties. These results effectively reject co-doping as a possible avenue for improving ceria conductivity. More fruitful outcomes are likely to be achieved in other intensely investigated areas such as the application of strain.^{32,105,106}

Appendix

A The DIPPIM model

In this section we provide a brief description of dipole polarizable ionic model (DIPPIM) potential employed in this work. The reader is referred to ref. 107–109 and references therein for further information concerning the form of the potential. This model has been previously used to study doped ceria and other oxides,^{22,64,66–68} as well as fluoride systems.^{69,70} In DIPPIM the various ionic species that form part of the simulation are assigned their formal valence charges (Ce^{4+} , RE^{3+} , and O^{2-}). The model also includes the polarization effects that result from the induction of dipoles on the ions. The potential is constructed from four components, the first three of which are

purely pairwise additive. The DIPPIM components are charge-charge, dispersion, overlap repulsion and polarization. The Coulombic interactions (charge-charge) are described by

$$V^{\text{qq}} = \sum_{i \leq j} \frac{q_i q_j}{r_{ij}} \quad (3)$$

where q_i is the *formal* charge on ion i . Dispersion interactions (eqn (4)) include dipole-dipole and dipole-quadrupole terms. Those terms in bold italic in eqn (4) and subsequent formulae were part of the fitting process described in Appendix B.

$$V^{\text{disp}} = - \sum_{i \leq j} \left[\frac{f_6^{ij}(r_{ij}) \mathbf{C}_6^{ij}}{r_{ij}^6} + \frac{f_8^{ij}(r_{ij}) \mathbf{C}_8^{ij}}{r_{ij}^8} \right] \quad (4)$$

Here \mathbf{C}_6^{ij} and \mathbf{C}_8^{ij} are the dipole-dipole and dipole-quadrupole dispersion coefficients, respectively. The f_n^{ij} are Tang-Toennies damping functions^{110,111} which are added in order to describe the short-range penetration correction to the asymptotic dispersion term and are expressed as follows:

$$f_n^{ij}(r_{ij}) = 1 - e^{b_n^{ij} r_{ij}} \sum_{k=0}^n \frac{(b_n^{ij} r_{ij})^k}{k!} \quad (5)$$

The short range repulsive term (eqn (6)) is approximately exponential in the region of physical interionic separations. The full expression used also includes a Gaussian function which acts as a steep repulsive wall and accounts for the anion hard core. This extra term is used in cases where there are highly polarizable ions (*e.g.* oxygen) to avoid instability problems at very small anion-cation separations.¹⁰⁹

$$V^{\text{rep}} = \sum_{i \leq j} \frac{\mathbf{A}^{ij} e^{-a^{ij} r_{ij}}}{r_{ij}} + \sum_{i \leq j} \mathbf{B}^{ij} e^{-b^{ij} r_{ij}^2} \quad (6)$$

As its name indicates, the polarization part of the DIPPIM potential incorporates dipolar effects only

$$V^{\text{pol}} = \sum_{i,j} \left(q_i \mu_{j,\alpha} f_4^{ij}(r_{ij}) - q_j \mu_{i,\alpha} f_4^{ji}(r_{ij}) \right) \mathbf{T}_\alpha^{(1)}(\mathbf{r}_{ij}) - \sum_{i,j} \mu_{i,\alpha} \mu_{j,\beta} \mathbf{T}_{\alpha\beta}^{(2)}(\mathbf{r}_{ij}) + \sum_i \frac{1}{2\alpha_i} |\mu_i|^2 \quad (7)$$

Here α_i is the polarizability of ion i , μ_i are the dipoles and $\mathbf{T}^{(1)}$ and $\mathbf{T}^{(2)}$ are the charge-dipole and dipole-dipole interaction tensors:

$$\mathbf{T}_\alpha^{(1)}(\mathbf{r}) = -r_\alpha/r^3 \quad \mathbf{T}_{\alpha\beta}^{(2)}(\mathbf{r}) = (3r_\alpha r_\beta - r^2 \delta_{\alpha\beta})/r^5 \quad (8)$$

The instantaneous values of the dipole moments are obtained by minimization of this expression with respect to the dipoles of all ions at each MD time step. This ensures that we regain the condition that the dipole induced by an electrical field \mathbf{E} is $\alpha\mathbf{E}$ and that the dipole values are mutually consistent. The short-range induction effects on the dipoles are taken into account by the Tang-Toennies damping functions (f_4^{ij}) similar to those used to damp the dispersion interactions (eqn (5)) where b^{ij} determines the range at which the overlap of the charge densities affects the induced dipoles. The damping of these induction effects requires an additional pre-exponential

parameter, c^{ij} , which determines the strength of the ion response to this effect.

B Potential parameterization

A total of $19 \times 2 \times 2$ fluorite-structured supercells were used to fit this IP set. They included YSZ (1), ScSZ (1), ceria-zirconia (3), pure ceria (1), reduced ceria (1) and two configurations of composition $\text{Ce}_{0.5}\text{RE}_{0.5}\text{O}_{1.75}$ for each of the systems. Each model supercell was obtained from high temperature (2000 K) *ab initio* MD simulations that were run for a few picoseconds in order to reach structural equilibrium. The forces on each species were determined directly from each DFT calculation, and the dipoles were obtained from a Wannier analysis of the Kohn-Sham (KS) wave functions.¹¹² In each case, hybrid density functional theory (h-DFT) calculations using the Heyd, Scuseria, Ernzerhof (HSE06) functional,^{113,114} as implemented in the VASP code,¹¹⁵ were performed. The inclusion of a fraction of nonlocal Hartree-Fock exchange to standard DFT in functionals such as HSE is known to be necessary to correctly describe the electronic structure of lanthanide oxides, such as reduced ceria,^{54,55} due to the highly correlated f-electrons present in these elements. This DFT functional also represents an improvement over other more commonly used functionals like LDA (local density approximation) or GGA (generalized gradient approximation) in terms of a closer agreement to experimental lattice constants⁵⁴ in cases where there are no f-electrons present, *e.g.* YDC, LaDC, *etc.*

Although dispersion energies constitute only a small fraction of the total energy, they have a considerable influence on transition pressures and, in particular, on the material density, thus the lattice constant, and the stress tensor. However, the dispersion terms were not included in the initial fit due to the well known uncontrolled representation of dispersion within the framework of DFT.¹¹⁶ Instead, values for the \mathbf{C}_6^{ij} and \mathbf{C}_8^{ij} terms were determined from the dipole polarizabilities for each element that resulted from the initial potential fit. The α values thus obtained have been previously found to be in very good agreement with other theoretically derived values.^{68,117} The relationship between the dispersion coefficients and the dipole polarizability is given by the Slater-Kirkwood equation.^{118,119} The final values for the DIPPIM parameters were then obtained by fixing the values of the polarizabilities and dispersion terms in a last round of optimization and re-fitting. The final χ^2 values for fit were 0.216 for dipoles and 0.335 for forces. Table 3 presents the parameters for the DIPPIM interionic potential set that was obtained.

C Vacancy analysis

The vacancy analysis of fluorite structured materials probes the occupancy changes of the tetrahedral sites formed by the face centred cubic cation sublattice. These are the sites where the oxide ions and, thus, their vacancies are normally present. The oxygen vacancy analysis is performed making use of the fact that the cations in the systems under study do not diffuse, even at high temperatures. Thus, it is possible to specify the cation sublattice in terms of tetrahedra, each of which may be empty (vacancy) or occupied by an oxide anion. For a set of time-correlated instantaneous ionic configurations, *i.e.*, frames in an

Table 3 All values are in atomic units, except those corresponding to the ionic radii, which are given in angstroms (Å) and are shown in parentheses alongside the dipole polarizabilities α . The parameters $b_D^{O^{2-}-\square}$ and $b_D^{\square-O^{2-}}$ were given the same value. Here, \square represents a placeholder for the identity of the ionic species specified in a given column

Interaction	A^{ij}	a^{ij}	B^{ij}	b^{ij}	C_D^{ij}	C_G^{ij}	b_G^{ij}	b_G^{ij}
$O^{2-}-O^{2-}$	7.15	18.52	50 000	1.00	83	1240	1.30	1.70
$Ce^{4+}-O^{2-}$	82.20	1.19	50 000	1.55	47	595	1.50	1.96
$Zr^{4+}-O^{2-}$	89.79	1.29	50 000	1.75	21	271	1.62	2.10
$La^{3+}-O^{2-}$	102.63	1.25	50 000	1.30	57	731	1.46	1.88
$Ce^{3+}-O^{2-}$	100.02	1.25	50 000	1.20	71	902	1.47	1.90
$Nd^{3+}-O^{2-}$	94.24	1.25	50 000	1.36	56	709	1.49	1.94
$Sm^{3+}-O^{2-}$	87.79	1.25	50 000	1.38	49	630	1.51	1.97
$Gd^{3+}-O^{2-}$	79.98	1.25	50 000	1.38	23	293	1.54	2.00
$Y^{3+}-O^{2-}$	118.0	1.38	50 000	1.50	21	264	1.60	2.08
$Sc^{3+}-O^{2-}$	61.66	1.28	50 000	1.75	15	197	1.77	2.30

Ion	α	Radius (Å)	$b_D^{O^{2-}-\square}$	$c_D^{O^{2-}-\square}$	$c_D^{\square-O^{2-}}$
O^{2-}	13.97	1.38	2.18	3.03	—
Ce^{4+}	5.86	0.97	1.75	1.85	0.17
Zr^{4+}	2.38	0.84	1.74	1.56	-0.60
La^{3+}	7.51	1.16	1.50	1.43	-0.20
Ce^{3+}	9.72	1.143	1.59	1.71	0.05
Nd^{3+}	7.24	1.109	1.67	1.94	0.00
Sm^{3+}	6.28	1.079	1.67	1.97	-0.14
Gd^{3+}	2.56	1.053	1.69	1.75	-0.89
Y^{3+}	2.31	1.019	1.47	1.08	-0.60
Sc^{3+}	1.70	0.87	1.67	1.36	-0.39

MD simulation, one can determine which tetrahedral sites are empty. However, distinction must be made between the vibrations undergone by the oxide anions, which are large in amplitude at the temperatures of interest, and instances when a given oxide anion has truly vacated a given tetrahedron. This distinction is made by imposing the condition that a site be considered a vacancy only if it has been vacant for a period of at least two frames. The position of each vacancy is then defined as the centre of the tetrahedron formed by the average positions of the four surrounding cations. These positions can then be used to calculate partial radial distribution functions (RDFs), from which vacancy ordering in real space can be studied. Integration of the vacancy-vacancy RDF (g_{v-v}) peaks from zero out to the position r_c gives the vacancy-vacancy coordination number, n_{v-v} :

$$n_{v-v} = 4\pi\rho \int_0^{r_c} r^2 g_{v-v} dr \quad (9)$$

where ρ is the vacancy density in the simulation cell. This method has been previously used to study similar materials, such as $Zr_2Y_2O_7$ - Y_3NbO_7 ,⁶⁶ YDC^{22} and PbO_2 .^{109,120}

Acknowledgements

MB acknowledges the HPC-EUROPA2 project (project number 228398) with the support of the European Commission Capacities Area – Research Infrastructures Initiative for access to the computing resources at CINES in France. Calculations were performed on the Stokes supercomputer (allocations tcche026b and tcche031b) maintained by ICHEC and Kelvin maintained by TCHPC. GWW acknowledges Science Foundation Ireland

(PI Grant numbers 12/IA/1414 and 08/RFP/MTR1044). DM wishes to thank the Government of Ireland for an EMPOWER Post-doctoral Fellowship and is thankful to Profs. Harry Tuller and Bilge Yildiz for his recent appointment as visiting scientist at MIT. The authors also thank Prof. Paul A. Madden (Oxford) and Dr Jonathan Yates for helpful discussions.

References

- 1 C. R. Karger and W. Hennings, *Renewable Sustainable Energy Rev.*, 2009, **13**, 583–593.
- 2 IEA, *Distributed Generation in Liberalised Electricity Markets*, OECD Publishing, Paris, 2002.
- 3 IEA, *Combined Heat and Power*, OECD Publishing, Paris, 2008.
- 4 R. M. Ormerod, *Chem. Soc. Rev.*, 2003, **32**, 17–28.
- 5 Y. Guo, M. Bessaa, S. Aguado, M. C. Steil, D. Rembelski, M. Rieu, J.-P. Viricelle, N. Benameur, C. Guizard, C. Tardivat, P. Vernoux and D. Farrusseng, *Energy Environ. Sci.*, 2013, **6**, 2119–2123.
- 6 E. D. Wachsman, C. A. Marlowe and K. T. Lee, *Energy Environ. Sci.*, 2012, **5**, 5498–5509.
- 7 E. D. Wachsman and K. T. Lee, *Science*, 2011, **334**, 935–939.
- 8 H. Qin, Z. Zhu, Q. Liu, Y. Jing, R. Raza, S. Imran, M. Singh, G. Abbas and B. Zhu, *Energy Environ. Sci.*, 2011, **4**, 1273–1276.
- 9 J. C. Ruiz-Morales, D. Marrero-Lopez, M. Galvez-Sanchez, J. Canales-Vazquez, C. Savaniu and S. N. Savvin, *Energy Environ. Sci.*, 2010, **3**, 1670–1681.
- 10 D. J. L. Brett, A. Atkinson, N. P. Brandon and S. J. Skinner, *Chem. Soc. Rev.*, 2008, **37**, 1568–1578.
- 11 H. L. Tuller and A. S. Nowick, *J. Electrochem. Soc.*, 1975, **122**, 255–259.
- 12 H. L. Tuller and A. S. Nowick, *J. Phys. Chem. Solids*, 1977, **38**, 859–867.
- 13 I. Abrahams, X. Liu, S. Hull, S. T. Norberg, F. Krok, A. Kozanecka-Szmigiel, M. S. Islam and S. J. Stokes, *Chem. Mater.*, 2010, **22**, 4435–4445.
- 14 C. Sun, H. Li and L. Chen, *Energy Environ. Sci.*, 2012, **5**, 8475–8505.
- 15 A. Bogicevic, C. Wolverton, G. M. Crosbie and E. B. Stechel, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 2001, **64**, 014106.
- 16 A. Bogicevic and C. Wolverton, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 2003, **67**, 024106.
- 17 A. Navrotsky, P. Simoncic, H. Yokokawa, W. Chen and T. Lee, *Faraday Discuss.*, 2007, **134**, 171–180.
- 18 F. Pietrucci, M. Bernasconi, A. Laio and M. Parrinello, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 2008, **78**, 094301.
- 19 A. Navrotsky, *J. Mater. Chem.*, 2010, **20**, 10577–10587.
- 20 S. T. Norberg, S. Hull, I. Ahmed, S. G. Eriksson, D. Marrocchelli, P. A. Madden, P. Li and J. T. S. Irvine, *Chem. Mater.*, 2011, **23**, 1356–1364.
- 21 D. Marrocchelli, P. A. Madden, S. T. Norberg and S. Hull, *Chem. Mater.*, 2011, **23**, 1365–1373.

- 22 M. Burbano, S. T. Norberg, S. Hull, S. G. Eriksson, D. Marrocchelli, P. A. Madden and G. W. Watson, *Chem. Mater.*, 2012, **24**, 222–229.
- 23 C.-T. Chen, S. Sen and S. Kim, *Chem. Mater.*, 2012, **24**, 3604–3609.
- 24 D. Marrocchelli, S. R. Bishop and J. Kilner, *J. Mater. Chem. A*, 2013, **1**, 7673.
- 25 V. Butler, C. R. A. Catlow, B. E. F. Fender and J. H. Harding, *Solid State Ionics*, 1983, **8**, 109–113.
- 26 J. Kilner, *Solid State Ionics*, 1983, **8**, 201–207.
- 27 G. B. Balazs and R. Glass, *Solid State Ionics*, 1995, **76**, 155–162.
- 28 H. Hayashi, R. Sagawa, H. Inaba and K. Kawamura, *Solid State Ionics*, 2000, **131**, 281–290.
- 29 D. A. Andersson, S. I. Simak, N. V. Skorodumova, I. A. Abrikosov and B. Johansson, *Proc. Natl. Acad. Sci. U. S. A.*, 2006, **103**, 3518–3521.
- 30 B. Wang, R. J. Lewis and A. N. Cormack, *Acta Mater.*, 2011, **59**, 2035–2045.
- 31 J. L. Rupp, *Solid State Ionics*, 2012, **207**, 1–13.
- 32 M. Burbano, D. Marrocchelli and G. Watson, *J. Electroceram.*, 2013, 1–9.
- 33 T. Politova and J. Irvine, *Solid State Ionics*, 2004, **168**, 153–165.
- 34 J. van Herle, D. Seneviratne and A. McEvoy, *J. Eur. Ceram. Soc.*, 1999, **19**, 837–841.
- 35 N. Singh, O. Parkash and D. Kumar, *Ionics*, 2013, **19**, 165–170.
- 36 N. K. Singh, P. Singh, D. Kumar and O. Parkash, *Ionics*, 2012, **18**, 127–134.
- 37 S. Omar, E. D. Wachsman, J. L. Jones and J. C. Nino, *J. Am. Ceram. Soc.*, 2009, **92**, 2674–2681.
- 38 S. Omar, E. D. Wachsman and J. C. Nino, *Appl. Phys. Lett.*, 2007, **91**, 144106.
- 39 X. Sha, Z. Lü, X. Huang, J. Miao, L. Jia, X. Xin and W. Su, *J. Alloys Compd.*, 2006, **424**, 315–321.
- 40 X. Sha, Z. Lü, X. Huang, J. Miao, Z. Ding, X. Xin and W. Su, *J. Alloys Compd.*, 2007, **428**, 59–64.
- 41 S. Dikmen, H. Aslanbay, E. Dikmen and O. Sahin, *J. Power Sources*, 2010, **195**, 2488–2495.
- 42 X. Guan, H. Zhou, Z. Liu, Y. Wang and J. Zhang, *Mater. Res. Bull.*, 2008, **43**, 1046–1054.
- 43 J. Ayawanna, D. Wattanasiriwech, S. Wattanasiriwech and P. Aungkavattana, *Solid State Ionics*, 2009, **180**, 1388–1394.
- 44 P. P. Dholabhai, J. B. Adams, P. A. Crozier and R. Sharma, *J. Mater. Chem.*, 2011, **21**, 18991–18997.
- 45 J. Ralph, J. Przydatek, J. Kilner and T. Seguelong, *Ber. Bunsen-Ges.*, 1997, **101**, 1403–1407.
- 46 R. M. Kasse and J. C. Nino, *J. Alloys Compd.*, 2013, **575**, 399–402.
- 47 D.-J. Kim, *J. Am. Ceram. Soc.*, 1989, **72**, 1415–1421.
- 48 R. Shannon, *Acta Crystallogr., Sect. A: Cryst. Phys., Diffr., Theor. Gen. Crystallogr.*, 1976, **32**, 751.
- 49 S. Omar, E. D. Wachsman and J. C. Nino, *Solid State Ionics*, 2006, **177**, 3199–3203.
- 50 A. Chroneos, B. Yildiz, A. Tarancon, D. Parfitt and J. A. Kilner, *Energy Environ. Sci.*, 2011, **4**, 2774–2789.
- 51 G. Balducci, M. S. Islam, J. Kašpar, P. Fornasiero and M. Graziani, *Chem. Mater.*, 2000, **12**, 677–681.
- 52 J. B. Goodenough, *Annu. Rev. Mater. Res.*, 2003, **33**, 91–128.
- 53 M. C. Gobel, G. Gregori, X. Guo and J. Maier, *Phys. Chem. Chem. Phys.*, 2010, **12**, 14351–14361.
- 54 J. L. F. Da Silva, M. V. Ganduglia-Pirovano, J. Sauer, V. Bayer and G. Kresse, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 2007, **75**, 045121.
- 55 R. Gillen, S. J. Clark and J. Robertson, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 2013, **87**, 125116.
- 56 M. V. Ganduglia-Pirovano, A. Hofmann and J. Sauer, *Surf. Sci. Rep.*, 2007, **62**, 219–270.
- 57 P. R. Keating, D. O. Scanlon and G. W. Watson, *J. Phys.: Condens. Matter*, 2009, **21**, 405502.
- 58 P. R. L. Keating, D. O. Scanlon, B. J. Morgan, N. M. Galea and G. W. Watson, *J. Phys. Chem. C*, 2012, **116**, 2443–2452.
- 59 P. R. L. Keating, D. O. Scanlon and G. W. Watson, *J. Mater. Chem. C*, 2013, **1**, 1093–1098.
- 60 M. Nolan, J. E. Fearon and G. W. Watson, *Solid State Ionics*, 2006, **177**, 3069–3074.
- 61 D. A. Andersson, S. I. Simak, B. Johansson, I. A. Abrikosov and N. V. Skorodumova, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 2007, **75**, 035109.
- 62 P. A. Madden and M. Wilson, *Chem. Soc. Rev.*, 1996, **25**, 339–350.
- 63 D. Marrocchelli, S. R. Bishop, H. L. Tuller and B. Yildiz, *Adv. Funct. Mater.*, 2012, **22**, 1958–1965.
- 64 D. Marrocchelli, M. Salanne and P. A. Madden, *J. Phys.: Condens. Matter*, 2010, **22**, 152102.
- 65 D. Marrocchelli, M. Salanne, P. A. Madden, C. Simon and P. Turq, *Mol. Phys.*, 2009, **107**, 443–452.
- 66 D. Marrocchelli, P. A. Madden, S. T. Norberg and S. Hull, *J. Phys.: Condens. Matter*, 2009, **21**, 405403.
- 67 M. Wilson, S. Jahn and P. A. Madden, *J. Phys.: Condens. Matter*, 2004, **16**, S2795.
- 68 M. Burbano, D. Marrocchelli, B. Yildiz, H. L. Tuller, S. T. Norberg, S. Hull, P. A. Madden and G. W. Watson, *J. Phys.: Condens. Matter*, 2011, **23**, 255402.
- 69 R. Heaton, R. Brookes, P. Madden, M. Salanne, C. Simon and P. Turq, *J. Phys. Chem. B*, 2006, **110**, 11454–11460.
- 70 M. Salanne, C. Simon, P. Turq and P. Madden, *J. Fluorine Chem.*, 2009, **130**, 38–44.
- 71 M. Salanne, D. Marrocchelli and G. W. Watson, *J. Phys. Chem. C*, 2012, **116**, 18618–18625.
- 72 G. J. Martyna, D. J. Tobias and M. L. Klein, *J. Chem. Phys.*, 1994, **101**, 4177–4189.
- 73 P. P. Ewald, *Ann. Phys.*, 1921, **369**, 253–287.
- 74 S. J. Hong and A. V. Virkar, *J. Am. Ceram. Soc.*, 1995, **78**, 433–439.
- 75 V. Grover, A. Banerji, P. Sengupta and A. Tyagi, *J. Solid State Chem.*, 2008, **181**, 1930–1935.
- 76 C.-i. Lee, Q.-L. Meng, H. Kaneko and Y. Tamaura, *J. Sol. Energy Eng.*, 2012, **135**, 011002.
- 77 R. Gerhardt-Anderson and A. S. Nowick, *Solid State Ionics*, 1981, **5**, 547–550.

- 78 K. Huang, M. Feng and J. B. Goodenough, *J. Am. Ceram. Soc.*, 1998, **81**, 357–362.
- 79 T. Zhang, P. Hing, H. Huang and J. Kilner, *Solid State Ionics*, 2002, **148**, 567–573.
- 80 C. Huang, W. Wei, C. Chen and J. Chen, *J. Eur. Ceram. Soc.*, 2011, **31**, 3159–3169.
- 81 S. Buyukkilic, T. Shvareva and A. Navrotsky, *Solid State Ionics*, 2012, **227**, 17–22.
- 82 T. Hisashige, Y. Yamamura and T. Tsuji, *J. Alloys Compd.*, 2006, **408–412**, 1153–1156.
- 83 S. Dikmen, P. Shuk and M. Greenblatt, *Solid State Ionics*, 1999, **126**, 89–95.
- 84 S. Grieshammer, B. O. H. Grope, J. Koettgen and M. Martin, *Phys. Chem. Chem. Phys.*, 2014, DOI: 10.1039/C3CP54811B.
- 85 B. C. H. Steele, *Solid State Ionics*, 2000, **129**, 95–110.
- 86 X.-D. Zhou, W. Huebner, I. Kosacki and H. U. Anderson, *J. Am. Ceram. Soc.*, 2002, **85**, 1757–1762.
- 87 C. Xia and M. Liu, *Solid State Ionics*, 2002, **152–153**, 423–430.
- 88 P. P. Dholabhai, S. Anwar, J. B. Adams, P. A. Crozier and R. Sharma, *Modell. Simul. Mater. Sci. Eng.*, 2012, **20**, 015004.
- 89 B. Grope, T. Zacherle, M. Nakayama and M. Martin, *Solid State Ionics*, 2012, **225**, 476–483.
- 90 J. Shemilt and H. Williams, *J. Mater. Sci. Lett.*, 1999, **18**, 1735–1737.
- 91 G.-B. Jung, T.-J. Huang and C.-L. Chang, *J. Solid State Electrochem.*, 2002, **6**, 225–230.
- 92 L. Aneflous, J. A. Musso, S. Villain, J.-R. Gavarri and H. Benyaich, *J. Solid State Chem.*, 2004, **177**, 856–865.
- 93 T. S. Zhang, J. Ma, L. B. Kong, S. H. Chan and J. A. Kilner, *Solid State Ionics*, 2004, **170**, 209–217.
- 94 I. E. Stephens and J. A. Kilner, *Solid State Ionics*, 2006, **177**, 669–676.
- 95 H. Lang, K. Kiinstler, M. Mangier and G. Tomandl, Solid Oxide Fuel Cells (SOFC VI): Proceedings of the Sixth International Symposium, 1999, p. 233.
- 96 P. Li, I.-W. Chen, J. E. Penner-Hahn and T.-Y. Tien, *J. Am. Ceram. Soc.*, 1991, **74**, 958–967.
- 97 M. Nakayama and M. Martin, *Phys. Chem. Chem. Phys.*, 2009, **11**, 3241–3249.
- 98 S. Hull, S. T. Norberg, I. Ahmed, S. G. Eriksson, D. Marrocchelli and P. A. Madden, *J. Solid State Chem.*, 2009, **182**, 2815–2821.
- 99 C. B. Gopal and A. van de Walle, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 2012, **86**, 134117.
- 100 S. Dikmen, *J. Alloys Compd.*, 2010, **491**, 106–112.
- 101 F.-Y. Wang, S. Chen and S. Cheng, *Electrochem. Commun.*, 2004, **6**, 743–746.
- 102 H. Yoshida, H. Deguchi, K. Miura, M. Horiuchi and T. Inagaki, *Solid State Ionics*, 2001, **140**, 191–199.
- 103 H. Yoshida, T. Inagaki, K. Miura, M. Inaba and Z. Ogumi, *Solid State Ionics*, 2003, **160**, 109–116.
- 104 S. T. Norberg, S. Hull, S. G. Eriksson, I. Ahmed, F. Kinyanjui and J. J. Biendicho, *Chem. Mater.*, 2012, **24**, 4294–4300.
- 105 A. Kushima and B. Yildiz, *ECS Trans.*, 2009, **25**, 1599–1609.
- 106 A. Kushima and B. Yildiz, *J. Mater. Chem.*, 2010, **20**, 4809–4819.
- 107 S. T. Norberg, I. Ahmed, S. Hull, D. Marrocchelli and P. A. Madden, *J. Phys.: Condens. Matter*, 2009, **21**, 215401.
- 108 P. A. Madden, R. Heaton, A. Aguado and S. Jahn, *THEO-CHEM*, 2006, **771**, 9–18.
- 109 M. J. Castiglione, M. Wilson and P. A. Madden, *J. Phys.: Condens. Matter*, 1999, **11**, 9009.
- 110 K. T. Tang and J. P. Toennies, *J. Chem. Phys.*, 1984, **80**, 3726–3741.
- 111 K. T. Tang and J. P. Toennies, *J. Chem. Phys.*, 2003, **118**, 4976–4983.
- 112 N. Marzari and D. Vanderbilt, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 1997, **56**, 12847–12865.
- 113 J. Heyd, G. E. Scuseria and M. Ernzerhof, *J. Chem. Phys.*, 2003, **118**, 8207–8215.
- 114 A. V. Krukau, O. A. Vydrov, A. F. Izmaylov and G. E. Scuseria, *J. Chem. Phys.*, 2006, **125**, 224106.
- 115 J. Paier, M. Marsman, K. Hummer, G. Kresse, I. C. Gerber and J. G. Angyan, *J. Chem. Phys.*, 2006, **124**, 154709.
- 116 W. Koch and M. C. Holthausen, *A Chemist's Guide to Density Functional Theory*, Wiley-VCH Verlag GmbH, Weinheim, Germany, 2001.
- 117 R. J. Heaton, P. A. Madden, S. J. Clark and S. Jahn, *J. Chem. Phys.*, 2006, **125**, 144104.
- 118 J. C. Slater and J. G. Kirkwood, *Phys. Rev.*, 1931, **37**, 682–697.
- 119 V. Haigis, M. Salanne, S. Simon, M. Wilke and S. Jahn, *Chem. Geol.*, 2013, **346**, 14–21.
- 120 M. J. Castiglione and P. A. Madden, *J. Phys.: Condens. Matter*, 2001, **13**, 9963.